

EFFECT OF AGE ON VARIATION IN PHYSICAL AND MECHANICAL PROPERTIES OF *Acacia mangium* PLANTED IN THAI NGUYEN

Duong Van Doan^{1*}, Nguyen Van Thai¹, Khong Van Manh²

¹TNU - University of Agriculture and Forestry

²Phu Luong Administration of Forestry

ARTICLE INFO	ABSTRACT
Received: 08/10/2020 Revised: 06/01/2021 Published: 14/01/2021	This study aimed to investigate the effect of age on some physical and mechanical properties of <i>Acacia mangium</i> planted in Thai Nguyen province such as air-dry density (AD), modulus of rupture (MOR), and modulus of elasticity (MOE). The small specimens with dimensions of 20 (radial) × 20 (tangential) × 320 (longitudinal) mm were cut at breast height of 7-, 10-, 14-year-old sample trees. The mean values of AD at 12% moisture content of 7-, 10-, 14-year-old <i>A. mangium</i> were 0.48, 0.51, and 0.53 g/cm³, respectively. The mean values of MOR of 7-, 10-, 14-year-old <i>A. mangium</i> were 64.38, 71.59, and 73.46 MPa, respectively, while these values of MOE were 7.31, 8.77, and 9.10 GPa, respectively. AD had a significant positive linear relationship with mechanical properties at all age levels. This suggests that AD could be a useful parameter to predict static bending strength of <i>A. mangium</i> wood. AD, MOR, and MOE exhibited a considerably increasing trend from age 7 to age 10 before stabilizing to age 14. This result will be an important reference for forest growers whether to extent planting time of <i>A. mangium</i> after 10 years or not.
KEYWORDS Wood science <i>Acacia mangium</i> Air-dry density Tree age MOE MOR	

ẢNH HƯỞNG CỦA TUỔI ĐẾN SỰ BIẾN ĐỔI CÁC TÍNH CHẤT VẬT LÝ VÀ CƠ HỌC CỦA GỖ KEO TẠI TƯỢNG (*Acacia mangium*) TRỒNG TẠI THÁI NGUYÊN

Dương Văn Đoàn^{1*}, Nguyễn Văn Thái¹, Khổng Văn Mạnh²

¹Trường Đại học Nông Lâm – ĐH Thái Nguyên

²Hạt Kiểm lâm huyện Phú Lương, tỉnh Thái Nguyên

THÔNG TIN BÀI BÁO	TÓM TẮT
Ngày nhận bài: 08/10/2020 Ngày hoàn thiện: 06/01/2021 Ngày đăng: 14/01/2021	Nghiên cứu này nhằm điều tra ảnh hưởng của tuổi đến một số tính chất vật lý và cơ học của gỗ Keo tại tượng trồng tại Thái Nguyên như: khối lượng thể tích (AD), độ bền uốn tĩnh (MOR), và mô đun đàn hồi uốn tĩnh (MOE). Các mẫu gỗ có kích thước 20 (xuyên tâm) × 20 (tiếp tuyến) × 320 (dọc thớ) mm được cắt từ vị trí ngang ngực của các cây mẫu ở tuổi 7, 10, và 14. Kết quả nghiên cứu đã chỉ ra rằng: giá trị trung bình AD ở độ ẩm 12% của Keo tại tượng tuổi 7, 10, và 14 lần lượt là 0,48 g/cm³, 0,51 g/cm³, và 0,53 g/cm³. Giá trị trung bình MOR của gỗ Keo tại tượng tuổi 7, 10, và 14 lần lượt là 64,38 MPa, 71,59 MPa, và 73,46 MPa, trong khi đó giá trị MOE lần lượt là 7,31 GPa, 8,77 GPa, và 9,10 GPa. AD có mối tương quan dương rõ ràng với các tính chất cơ học ở tất cả các tuổi trong nghiên cứu này. Điều này gợi ý rằng AD có thể là một thông số hữu ích để dự đoán được các tính chất cơ học của gỗ Keo tại tượng trồng tại Thái Nguyên. Cả AD, MOR, và MOE đã tăng lên đáng kể từ tuổi 7 đến tuổi 10 nhưng sau đó tăng chậm dần và có xu hướng không thay đổi đến tuổi 14. Kết quả của nghiên cứu này là tài liệu tham khảo quan trọng cho người trồng rừng Keo tại tượng khi quyết định có nên kéo dài thời gian trồng sau 10 năm hay không.
TỪ KHÓA Khoa học gỗ Keo tại tượng Khối lượng thể tích Tuổi cây MOE MOR	

DOI: <https://doi.org/10.34238/tnu-jst.3689>

* Corresponding author. Email: duongvandoan@tuaf.edu.vn

1. Introduction

Acacia mangium Willd. is one of the important tree species planted popularly in Vietnam because of its wide applicability with a variety of forest sites, straight stem, and faster growth than *Acacia auriculiformis* and *Uro Eucalyptus* [1]. According to the documentary No. 30/2018/TT-BNNPTNT of the Ministry of Agriculture and Rural Development issued on November 16, 2018 about the list of major forestry plant species, *A. mangium* is classified into the list of the main species for planting forest in Vietnam [2]. Currently, *A. mangium* wood is mainly used as raw materials for pulp production, particle board, MDF board, and peeled veneers [3]. *A. mangium* is a fast-growing species that produces low wood quality because of the present of juvenile wood, which can cause serious problems [4].

Age of tree is one of the important factors affecting to variation in wood properties. The trend of variation depends on some factors such as species, growth conditions, and age of tree. There were some studies regarding to evaluate the effect of age on variation in wood properties of *A. mangium*. Makino et al. [4] evaluated the wood properties of 5- and 7-year-old *A. mangium* planted in West Java, Indonesia. The mean basic density and compression strength for 5-year-old trees were 0.42 g/cm³ and 30.0 MPa, and for 7-year-old trees were 0.45 g/cm³ and 32.8 MPa, respectively. Chowdhury et al. [5] studied the effects of age (10-, 15-, and 20-year-old) on physical properties of *A. mangium* trees grown in Bangladesh. The authors reported that the mean basic density of *A. mangium* among different age groups was 0.52-0.60 g/cm³, the maximum being observed in wood from 20-y-old trees and the minimum in wood from 10-year-old trees. In Vietnam, the researches reporting effect of age on variation in physical and mechanical properties of *A. mangium* wood is limited. Trinh [3] reported effect of harvested age on some physical and mechanical properties of peeled veneer of *A. mangium*. This study showed that the basic density of the peeled veneers increased with the age of the trees. The mean basic density and modulus of elasticity of *A. mangium* peeled veneers at the age of 6, 9, 14 were 0.39, 0.43, and 0.51 g/cm³ for basic density, respectively and 8.66, 10.87, and 10.93 GPa for modulus of elasticity, respectively.

Information on wood structure and properties, and the influence of tree age on these, is required for better utilisation. In this study, we assessed the effects of tree age on some physical and mechanical properties of *A. mangium* trees planted in Thai Nguyen, Vietnam. The results of this study provide information to forest growers for selecting approximate time to harvest *A. mangium* wood.

2. Materials and Methods

2.1. Materials

A total of fifteen trees of 7-, 10-, and 14-year-old *A. mangium* planted in Phu Luong, Thai Nguyen, Vietnam was collected in this study (5 trees/age level). The latitude and longitude of 7-, 10-, and 14-y-old planted forests are N02408224 and E00417280, N02402724 and E00414187, N02402646 and E00414070, respectively. The sample trees were selected basing on straight trunks, normal branching, and no signs of any diseases or pest symptoms. Diameter at breast height (1.3 m above the ground) as well as the total stem height for each tree was measured. The detail information of each tree is given in Table 1. The north and south sides of each tree were marked before felling.

Method of cutting specimens for experiments is presented in Figure 1. From each tree, 50-cm-long logs were cut from 1.05 to 1.55 m height from above the ground and air-dried in two months. From each log, small specimens (20 × 20 × 320 mm, Radial × Tangential × Longitudinal) were cut at three distances from pith (10, 50, and 90 % of the radial length from pith) on four sides (north, south, east, west) for measuring air-dry density (AD), modulus of rupture (MOR), and modulus of elasticity (MOE) as described in Figure 1. For 7-year-old trees, in each radial direction, small specimens were only cut at two positions: near the pith and near

the bark corresponding to 10 and 90% radial positions because of small diameter. The specimens were conditioned in a room at a constant temperature (20°C) and relative humidity (60%) to constant weight.

Table 1. Diameter and height of sample trees

Trees	D _{1.3} (cm)	H _{vn} (m)
Age 7		
1	14.0	14.0
2	15.6	16.0
3	16.6	15.0
4	17.2	17.5
5	15.9	17.0
Age 10		
6	23.1	17.5
7	24.6	16.8
8	25.3	16.2
9	23.9	18.6
10	22.7	19.8
Age 14		
11	18.8	16.2
12	24.2	16.5
13	27.4	17.0
14	24.5	21.0
15	23.6	20.4

Note: D_{1.3} - diameter at breast height (at 1.3 m above the ground), H_{vn} - tree height

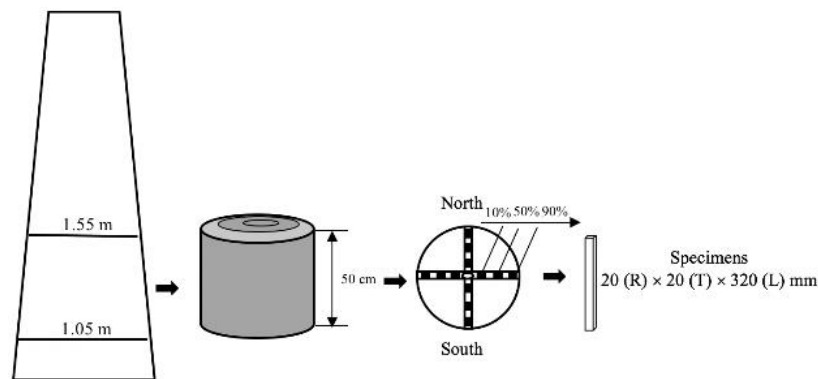


Figure 1. Method of cutting specimens for experiment from each tree

2.2. Measuring wood properties

AD, MOR, and MOE were assessed in accordance with Vietnamese Industrial Standards (TCVN) as described by Duong et al. [6]. AD was determined in according TCVN 8048-2:2009 (ISO 3131:1975), while MOR and MOE were measured in according to TCVN 8048-3:2009 (3133:1975) and TCVN 8048-4:2009 (ISO 3349:1975), respectively. Twenty samples were randomly chosen to test moisture content (MC) after measuring mechanical properties. The average MC of the test specimens was $12 \pm 0.18\%$.

2.2. Data analysis

The data in this study was analysed by using the R software (R Core Team) version 4.0.2 [7]. Tukey-Kramer HSD test was used for comparing wood properties among the age groups.

3. Results and Discussions

3.1. Variation in AD from the pith to bark

Table 2 presents the mean values of AD at 10, 50, and 90 % radial length from the pith to bark in trees of *Acacia mangium* 7-, 10-, and 14-year-old planted in Thai Nguyen. Results of ANOVA analysis are also presented in Table 2 to exam that there are significant differences in AD among radial positions or not.

The mean AD for 7-, 10-, and 14-y-old trees varied from 0.45 to 0.51 g/cm³, 0.47 to 0.54 g/cm³, and 0.48 to 0.56 g/cm³, respectively (at MC 12%). The findings of the present study are in agreement to those in literature. Phi [1] reported an AD of 0.43 – 0.56 g/cm³ of *A. mangium* grown in Binh Duong, Vietnam. In addition, Chowhury et al. [5] reported the mean AD of 10-year-old *A. mangium* planted in Bangladesh was 0.52 g/cm³ that is similar with AD observed for trees of age 10 in this study.

Table 2. Mean of air-dry density (g/cm³) and results of statistical analysis among radial positions in different ages

Age	Radial position (%)			p-value
	10	50	90	
7	0.45 ^b ± 0.04		0.51 ^a ± 0.02	***
10	0.47 ^b ± 0.05	0.53 ^a ± 0.03	0.54 ^a ± 0.03	***
14	0.48 ^b ± 0.05	0.55 ^a ± 0.03	0.56 ^a ± 0.03	***

Note: ^{a,b,c} Mean with different superscript within a row significant difference; ***: $p < 0.001$

The result of ANOVA analysis showed that AD for 7-y-old *A. mangium* wood was the lowest near the pith and the highest near the bark. In 10- and 14-y-old trees, the radial variation pattern for AD was similar. AD increased rapidly from the pith to position of 50% radial length before becoming constant towards the bark (Table 2). The radial pattern of variation from pith to periphery of AD has been reported for *A. mangium* wood. Makino et al. [4] reported the radial variation for basic density of 5- and 7-y-old *A. mangium* trees planted in Indonesia. Basic density gradually increased to about 6 cm from the pith before stabilizing. Kim et al. [8] reported a similar pattern of AD for *Acacia hybris* planted in northern Vietnam. On other hand, Wahyudi et al. [9] reported a nearly constant basic density of *Azadirachta excelsa* from pith to bark. Based on the present results and previous reports, radial variation of AD depends on species.

3.2. Radial variations in mechanical properties

Table 3 presents the mean mechanical properties at 10, 50, and 90% radial length from the pith of 7-, 10-, and 14-year-old *A. mangium* trees planted in Thai Nguyen. The mean MOR for 7-year-old trees at 10 and 90% radial length was 56.73 and 73.05 MPa. The mean MOR for 10- and 14-year-old trees varied from 61.94 to 76.16 MPa and from 65.13 to 77.99 MPa, respectively. Obtained results in the present study were similar to those in previous studies. Shari et al. [10] investigated the static bending strength of 6-y-old *A. mangium* trees planted in different sites. This study reported that the overall MORs of *A. mangium* planted in Indonesia, Malaysia, and Thailand were 75.02, 68.15, and 80.54 MPa, respectively.

The mean MOE for 7-, 10-, and 14-year-old varied from 6.56 to 8.17 GPa, 7.45 to 9.55 GPa, and 7.75 to 10.14 GPa, respectively. Shari et al. [10] also reported that the mean MOE of 6-y-old *A. mangium* trees planted in Indonesia, Malaysia, and Thailand were 6.73, 6.29, and 6.17 GPa, respectively.

Table 3. Mean of mechanical properties and results of statistical analysis among radial positions in different ages

Mechanical properties	Age	Radial position from pith (%)			p-value
		10	50	90	
MOR (MPa)	7	56.73 ^b ± 11.14		73.05 ^a ± 6.47	***
	10	61.94 ^b ± 14.67	76.39 ^a ± 11.96	76.16 ^a ± 10.00	**
	14	65.13 ^b ± 15.62	77.75 ^a ± 13.30	77.99 ^a ± 9.98	**
MOE (GPa)	7	6.56 ^b ± 0.71		8.17 ^a ± 0.94	***
	10	7.45 ^b ± 1.26	9.29 ^a ± 1.07	9.55 ^a ± 0.65	***
	14	7.75 ^b ± 1.10	9.55 ^a ± 1.07	10.14 ^a ± 0.88	***

Note: Note: ^{a,b,c} Mean with different superscript within a row significant difference;

: $p < 0.01$; *: $p < 0.001$

The radial variation patterns for MOR and MOE were similar to those for AD (Table 3). In age of 7, the result of statistical analysis showed that there was a significant difference in MOR between two positions (near the pith and near the bark). In 10- and 14-y-old trees, MOR and MOE increased considerably to the middle position before remaining constant value forward to outside (Table 3). Fujimoto et al. [11] reported that the compression strength increased from the pith to 5 cm, after which it was almost constant in 30-y-old *A. mangium*. This pattern is also seen in other hardwood species. Machado et al. [12] investigated the radial variation in MOR and MOE of *Acacia melanoxylon* wood. Authors showed that MOR and MOE increased rapidly from pith to 50% radial position before stabilizing. This trend may be contributable to the thicker walls of fibers in the mature wood than those in the juvenile wood.

3.3. Effect of age on variation in AD, MOR, and MOE

The mean AD for 7-, 10-, and 14-y-old *A. mangium* trees was 0.48, 0.51, and 0.53 g/cm³, respectively (Table 4). The AD increased with increasing tree age. The average AD of 14-year-old trees increased about 4% compared to that of 10-year-old trees and about 10% compared 7-year-old trees. However, the analysis of variance indicated that, there is only significant difference between AD of age 7 and AD of age 10 and 14, while no significant difference was found between AD of age 10 and AD of age 14.

Table 4. Physical and mechanical properties in different ages, ANOVA, and Tukey test results

Wood properties	Age			p-value
	7	10	14	
AD (g/cm ³)	0.48 ^b ± 0.04	0.51 ^a ± 0.05	0.53 ^a ± 0.05	***
MOR (MPa)	64.38 ^b ± 10.55	71.59 ^a ± 13.92	73.46 ^a ± 14.44	**
MOE (GPa)	7.31 ^b ± 1.15	8.77 ^a ± 1.38	9.10 ^a ± 1.43	***

Note: ^{a,b,c} Mean with different superscript within a row significant difference;

: $p < 0.01$; *: $p < 0.001$

The mean MOR for 7-, 10-, and 14-y-old *A. mangium* trees was 64.38, 71.59, and 73.46 MPa, respectively. The mean MOE for 7-, 10-, and 14-y-old *A. mangium* trees was 7.31, 8.77, and 9.10 GPa, respectively (Table 4). The analysis of variance also indicated that there was no significant difference in MOR and MOE between age 10 and age 14, while tree age did have a significant effect to MOR and MOE from 7 to 10 years. The results in this study will be an important reference for forest growers whether to extent planting time of *A. mangium* after 10 years or not.

3.4. The relationship between AD and mechanical properties

Coefficients of correlations (r) for relationship between AD and mechanical properties of *A. mangium* planted in Thai Nguyen are summarized in Table 5. AD had significant ($p < 0.001$)

positive linear correlations with MOR in all age levels. Correlation coefficient between AD and MOR is 0.72 when combined ages (Figure 2). AD had also significant positive linear relationships at the 0.001 confidence level with MOE in all age levels (Table 5). For combined ages, the value of correlation coefficient between AD and MOE is 0.78 (Figure 3). The above results suggest that AD can be considered to be a powerful indicator for predicting the static bending strength of *A. mangium* planted in Thai Nguyen. Prediction models of mechanical properties (MOR, MOE) for *A. mangium* clear wood in different ages and combined ages are presented in Table 5.

Table 5. Prediction models of static properties (MOR, MOE) for *Acacia mangium* wood

Modelling	Age	Equation	<i>r</i>	<i>p</i> -value
MOR (MPa) (~AD)	7	$MOR = 210.89 \times AD - 36.05$	0.79	***
	10	$MOR = 243.99 \times AD - 53.74$	0.82	***
	14	$MOR = 156.61 \times AD - 9.54$	0.65	***
	Combined ages	$MOR = 193.44 \times AD - 28.28$	0.72	***
MOE (GPa) (~AD)	7	$MOE = 21.20 \times AD - 2.78$	0.73	***
	10	$MOE = 21.95 \times AD - 2.50$	0.75	***
	14	$MOE = 20.13 \times AD - 1.57$	0.72	***
	Combined ages	$MOE = 23.05 \times AD - 3.22$	0.78	***

Note: ***: $p < 0.001$

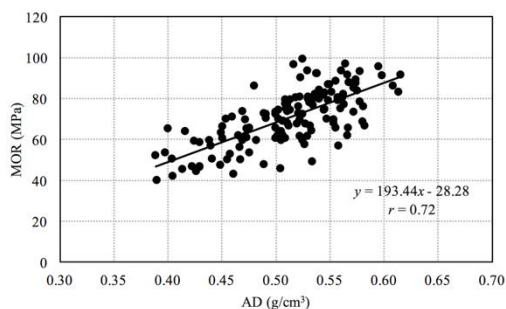


Figure 2. Relationship between air-dry density (AD) and modulus of rupture (MOR) for combined ages

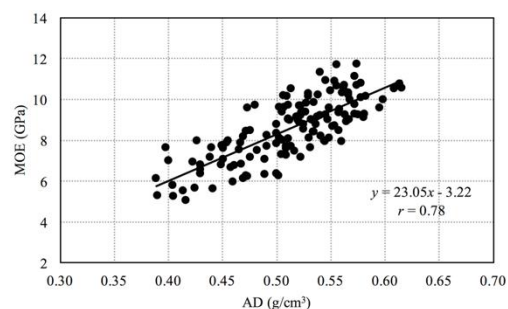


Figure 3. Relationship between air-dry density (AD) and modulus of elasticity (MOE) for combined ages

Wood density is an important indicator of the static bending strength properties of wood. The present results are comparable with those reported by Makino et al. [4] who found the positive correlation of basic density with mechanical properties of *A. mangium* planted in Indonesia. In other hardwood species, Duong and Matsumura [13] found strong positive correlations of AD with MOR ($r = 0.84$) and MOE ($r = 0.72$) at MC about 12% in *Melia azedarach* planted in Son La, Vietnam. Positive linear relationships between AD and mechanical properties were also reports by Machado et al. [12] for *Acacia melanoxylon* wood.

4. Conclusions

- Tree age had significantly affected on physical and mechanical properties investigated in this study. AD, MOR, and MOE increased rapidly from age 7 to age 10 before stabilizing to age 14.
- In radial direction, AD, MOR, and MOE were lower near the pith and higher near the bark in all age levels. In 10- and 14-year-old, wood properties determined in this study increased considerably from pith to the middle position before remaining constant value forward to outside.
- AD had a significant positive linear relationship with mechanical properties (MOR, MOE). Therefore, AD can be considered to be a powerful indicator for predicting the static bending strength of *A. mangium* planted in Thai Nguyen.

REFERENCES

- [1] H. H. Phi, "Genetic control on wood mechanical properties of *Acacia mangium* in the second generation progenytests," *Science and Technology Journal of Agriculture and Rural Development*, vol. 14, pp. 128-135, 2018.
- [2] Ministry of Agriculture and Rural Development, *The list of major forest plant species, recognition of varieties and seed sources, management of materials of major forest plant varieties*. No. 30/2018/TT-BNNPTNT, Ha Noi, 2018.
- [3] H. M. Trinh, "Effect of harvested age on some physical and mechanical properties of peeled veneer from *Acacia mangium* Willd.," *Journal of Forestry Science and Technology*, vol. 6, pp. 134-141, 2018.
- [4] K. Makino, F. Ishiguri, I. Wahyudi, Y. Takashima, K. Iizuka, S. Yokota, and N. Yoshizawa, "Wood properties of young *Acacia mangium* trees planted in Indonesia," *Forest Product Journal*, vol. 62, no. 2, pp. 102-106, 2012.
- [5] M. Q. Chowdhury, M. I. Shams, and M. Alam, "Effects of age and height variation on physical properties of mangium (*Acacia mangium* Willd.) wood," *Australian Forestry*, vol. 68, no. 1, pp. 17-19, 2005.
- [6] V. D. Duong, T. T. H. Tran, T. K. H. Duong, T. Y. Trieu, and D. T. Nguyen, "Variation in wood density and mechanical properties of *Manglietia conifera* Dandy planted in Na Ri, Bac Kan," *Journal of Forestry Science and Technology*, vol. 9, pp. 121-126, 2020.
- [7] R Core Team, "R: A language and environment for statistical computing," R Foundation for Statistical Computing, Vienna, Austria. [Online]. Available: <https://www.R-project.org>. [Accessed Sept. 01, 2020].
- [8] T. K. Nguyen, M. Ochiishi, J. Matsumura, and K. Oda, "Variation in wood properties of six natural acacia hybrid clones in northern Vietnam," *Journal of Wood Science*, vol. 54, pp. 436-442, 2008.
- [9] I. Wahyudi, F. Ishiguri, K. Makino, H. Aiso, Y. Takashima, J. Ohshima, H. Iizuka, and S. Yokota, "Evaluation of xylem maturation and the effects of radial growth rate on anatomical characteristics and wood properties of *Azadirachta excelsa* planted in Indonesia," *Journal of the Indian Academy of Wood Science*, vol. 13, no. 2, pp. 138-144, 2016.
- [10] M. H. Sahri, Z. Ashaari, R. A. Kader, and A. L. Mohmod, "Physical and mechanical properties of *Acacia mangium* and *Acacia auriculiformis* from different provenances," *Pertanika Journal of Tropical Agricultural Science*, vol. 21, no. 2, pp. 73-81, 1998.
- [11] T. Fujimoto, H. Akutsu, and T. Takizawa, "Several wood properties of plantation-grown *Acacia* species," *Journal of the Hokkaido Forest Products Research Institute*, vol. 16, no. 2, pp. 6-10, 2002.
- [12] J. L. Machado, J. L. Louzada, A. J. A. Santos, L. Nunes, O. Anjos, J. Rodrigues, R. M. S. Simoes, and H. Pereira, "Variation of wood density and mechanical properties of blackwood (*Acacia melanoxylon* R. Br.)," *Materials and Design*, vol. 56, pp. 975-980, 2014.
- [13] V. D. Duong, and J. Matsumura, "Within-stem variations in mechanical properties of *Melia azedarach* planted in northern Vietnam," *Journal of Wood Science*, vol. 64, pp. 329-337, 2018.